



2873 22nd St SE
Salem, OR 97302

Tel: 503.540.8114
Fax: 503.362.5597
www.oregonbl.com
ISO/IEC 17025:2017 Accredited Laboratory
NVLAP Code: 200826-0

May 30th, 2023

Riot Glass
17941 Brookshire Lane
Huntington Beach, CA 93647
ATTN: Brad Campbell

Dear Mr. Campbell:

In accordance with your instructions, Oregon Ballistic Laboratories conducted Ballistic Resistance testing (V_0) on one samples.

The sample was tested in accordance with UL 752 Level 3 in an indoor range with the muzzle of the test barrel mounted 16.5 feet from the target and positioned to produce 0-degree obliquity impacts. Four Oehler model 57 infrared velocity light screens, in conjunction with two HP 5315A time-based frequency counters, were placed such that projectile velocity was measured 8.25 feet from the target. Penetrations were determined by examination of a piece of 1/8" corrugated cardboard witness mounted 18 inches behind and parallel to the test sample. Results for all testing performed for this purpose are summarized in the following table.

Test Sample				Ballistic Threat				Results	
OBL No.:	Model No.:	Weight (lbs.)	Average Thickness (in.)	Projectile	Shots	Velocity (fps)		Penetrations	Pass/Fail
						Min.	Max.		
35333	AP100	6.31	1.021	.44 Mag SWCGC	3	1397	1415	0	<u>PASS</u>

*Data shown in the table represents fair impacts only.

This report pertains only to the samples tested and may not be modified or edited in any way. This report may not be used to claim product certification, approval, or endorsement by NVLAP, NIST, or any federal government agency. Samples will be maintained at Oregon Ballistic Laboratories for 30 days and discarded unless other instructions are received. If you have any further questions or concerns, don't hesitate to contact us.

Darius Nuttbrock
Ballistic Test Director
Oregon Ballistic Laboratories
503.689.5134
Email: dnuttbrock@oregonbl.com

This report pertains only to the samples tested and may not be modified or edited in any way.

This report may not be used to claim product certification, approval, or endorsement by NVLAP®, NIST, or any Federal Government agency.

Contributors to measurement of uncertainty:

Velocity- tape measure used for screen spacing, Measurement of uncertainty of frequency counters

BALLISTIC RESISTANCE TEST - V₀

Customer: Riot Glass
 OBL ID#: 35333
 Date Rcv'd: 4/27/2023
 Test Date: 5/11/2023
 Purchase Order:

TEST SAMPLE

Model No.:	AP100	Size (in.):	12 x 12
Sample No.:	2	Weight (lb.):	6.31
Lot No.:	N/A	Thickness:	1.020 1.021 1.021 1.023
Plies:	N/A	Avg. Thk. (in):	1.021
Description:	Ballistic Transparency		

RANGE SET-UP

Range to Target:	16.5 ft.	Range #:	3	Pre Test:	CLAY CALIBRATION NOT REQUIRED
Screen Dist. Vel. 1 (ft.):	5	Temperature:	71.9 °F	Clay Drops (mm):	
Screen Dist. Vel. 2 (ft.):	4	Bar. Pressure:	29.81 in. Hg	Drop Avg (mm):	
Screen 4 to target (ft):	N/A	Rel. Humidity:	44.0 %	Clay Temp °F:	
Primary Vel. Location:	8.25 ft. from target	Sample Temp.	Amb. °F	Clay Box #:	
Striking Velocity:	No	Recorder:	Jerhemi Stone	Post Test:	
Target to Witness:	18 in.	Gunner:	Nathan Myers	Clay Drops (mm):	
Witness Panel:	1/8" Corr. Cardboard			Drop Avg (mm):	
Backing Material:	N/A			Clay Temp °F:	
Obliquity:	0 Degrees				
Barrel:	.44 Mag/1:20/8"				

AMMUNITION

Projectile: .44 Mag 240gr. SWCGC RCBS 82042 Montana Bullet Works Powder: Accurate No. 2

STANDARDS / PROCEDURES

UL 752 Level 3 Required Velocity: 1350 fps + 135 fps

SHOT NO.	PROJECTILE WT. (gr.)	POWDER WT. (gr.)	TIME 1 μ s (10 ⁻⁶)	TIME 2 μ s (10 ⁻⁶)	VELOCITY 1 ft/s	VELOCITY 2 ft/s	AVERAGE VELOCITY	PENET. P/C	OBLIQUITY	CALIPER BFD	NOTES
1	239.9	11.9	3545	2818	1410	1419	1415	P	0°		
2	240.2	11.9	3548	2832	1409	1412	1411	P	0°		
3	239.6	11.9	3571	2869	1400	1394	1397	P	0°		


REMARKS:

P=Partial Penetration
 C=Complete Penetration
 UH=Unfair Hit
 Projectile Yaw Check: <5° for all velocity shots

TEST RESULTS:


Test sample satisfied the ballistic requirements given.

FOOTNOTES:



OREGON BALLISTIC LABORATORIES

OBL #35333 – Pre Test

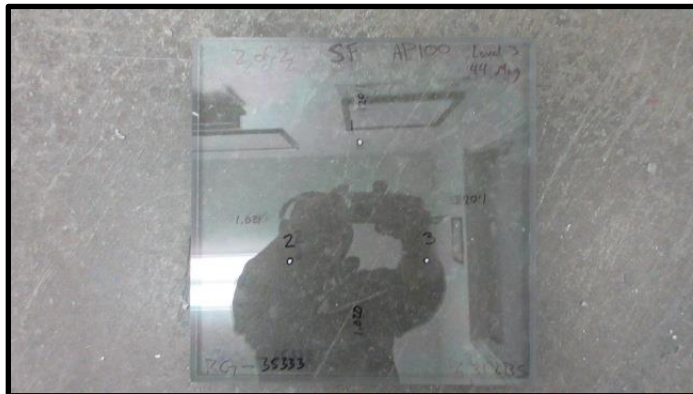

OBL #35333 – Post Test

